



Preparation, characterization and antibacterial applications of ZnAl-LDH with the diaminodecylphosphonic acid intercalation

Ziani Hanane, M 'Hamed Kaid, Ikhoul Djamila, Abdelkader Ammam, Didier Villemin

► To cite this version:

Ziani Hanane, M 'Hamed Kaid, Ikhoul Djamila, Abdelkader Ammam, Didier Villemin. Preparation, characterization and antibacterial applications of ZnAl-LDH with the diaminodecylphosphonic acid intercalation. South Asian Journal of Experimental Biology, 2021, 11 (5), pp.600-604. 10.38150/sajeb.11(5).p600-604 . hal-03510457

HAL Id: hal-03510457

<https://normandie-univ.hal.science/hal-03510457>

Submitted on 4 Jan 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Preparation, characterization and antibacterial applications of ZnAl-LDH with the diaminododecylphosphonic acid intercalation

Ziani Hanane¹, M'hamed Kaid^{1*}, Ikhou Djamila¹, Abdelkader Ammam¹, D. Villemin²

¹Laboratoire d'études physico-chimiques, Département de Chimie, Faculté des Sciences Université Dr Moulay Taher. BP 138. Ennasr. Saida

²LCMT, EnsiCaen, UMR CNRS 6507, Caen, France

ABSTRACT

Layered double hydroxides (LDHs) have been widely investigated in a wide range of applications in health, in the pharmaceutical industry and in the material of biotechnology industries. This material can be considered as a group of promising materials in the development of new health applications. The combination of phosphonic acid with LDHs material create a new hybrid material with new properties. In this work the synthesis of Zn/Al double layered hydroxides by chemical co-precipitation method (molar ration 2) and grafted with Diamino Dodecyl Phosphonic Acid (DDPA) via anion-exchange mechanism. The samples were characterized and confirmed by X-ray diffraction (XRD), and the presence of diamino dodecyl phosphonic acid (DDPA) was verified by Elemental analysis, BET analysis, and infrared spectroscopy. Both of the samples were found to be showing antibacterial activity. The zone diameters of Zn-Al-LDH were 40 mm and 25 mm for *Escherichia coli* (ATCC 25922) and *Streptococcus* (ATCC 25922) and 20 mm for *Bacillus* (ATCC 25922) whereas the same for hybrid LDH (Zn-Al-DDPA) were 43 mm, 32 mm and 25 mm for the same bacteria showing stronger antibacterial activity of the grafted material over the material itself. The experimental results confirm the application of Zn-Al-DDPA in the field of antibacterial activities and may offer a promising antibacterial elucidation to the society.

1. Introduction

Layered double hydroxides (LDHs) are one such potential inorganic matrices, containing sheets succession (Kadari et al., 2017) they are layered compounds by metal hydroxide sheet with positive charge and interlayer space filled with anion with negative electric charge. They can be expressed by the general formula $[M^{II}_{1-x} M^{III}_x (OH)_2]^{x+} [A^{n-}_{x/n} \cdot mH_2O]^{x-}$. (Cheng et al., 2019) in which M^{2+} (Mg^{2+} , Ca^{2+} , Zn^{2+} , Cu^{2+} , Co^{2+} , Ni^{2+} , etc.) and M^{3+} (Al^{3+} , Fe^{3+} ,

Ga^{3+} , Cr^{3+}) are divalent and trivalent cations and An^- (Cl^- , CO_3^{2-} , NO_3^- , etc.) is an anion, thus having positive or negative charge layers (Marcato et al., 2013; Totaro et al., 2018). Depending up on the nature of cations and their molar ratios $M(II)/M(III)$, and so the anions type, many compounds, with vast difference, can be obtained. The range $0.2 \leq x \leq 0.33$ is generally acknowledged to be suitable for the synthesis of LDH compounds i.e. the ratio of M^{2+}/M^{3+} is in between 2:1 to 4:1 (Mishra et al., 2013; Zümreoglu et al., 2012). These anionic clays, has been

noticed to be of considerable uses due to their fascinating properties in compositional flexibility, anion and cation exchangeability, in many technologically in catalysis, separation technology, optics, medical science, low toxicity, superior biocompatibility, synthesis of films and coatings for anti-corrosion, sensing and antibacterial applications (Ryu et al., 2010; Chen et al., 2011; Mei et al., 2018; Mishra et al., 2018).

ZnAl hydroxides are effective antibacterial agents for bacteria such as *Escherichia coli* and *Staphylococcus aureus* due to the hydroxides ($-OH$) and the nature of the metallic cations, where Zn^{2+} is one of the most active ones, due to its strong oligodynamic features (Ferraris et al., 2016; Gohi et al., 2019). Moreover, Zn ions possess excellent antibacterial ability and were widely used as inorganic antibacterial agents (Hue et al., 2013; Wang et al., 2016). Also, many hybrid materials, organic hybrids, inorganic hybrids and organic-inorganic hybrids, have been tested and still have a lot of applications in biomedical science (Gohi et al., 2019).

Wang et al. (2013) studied the antibacterial and the antimicrobial activity of $Mg-Al-NO_3^-$

LDH with Ga^{3+} salicylidene-amino acid Schiff base complex intercalation. (Wang et al., 2013)

In previous works, we have prepared and characterized a new hybrid material (ZnAl-DDPA) by intercalating the double layered hydroxide synthesized in our laboratory (ZnAl-LDH) prepared by co-precipitation method using diamino dodecyl phosphonic acid (DDPA). In this work, *Streptococcus*, *Bacillus* (gram negative) and *E. Coli* (gram positive) antibacterial activity has been studied using a synthesized LDH and its hybrid material.

2. Experimental

2.1. Materials

The reagents used in this study were Zn Al-Cl and ZnAl-DDPA synthesized in the laboratory (Villemin et al., 2010; Kadari et al., 2017), the raw materials used were $ZnCl_2$ (Riedel-de Haën), $AlCl_3 \cdot 6H_2O$ (Panreac), $NaOH$ (99%, Riedel De Haen).

The bacterial stains used in this work are *Streptococcus* (ATCC 25922 gram negative) and *Bacillus* (ATCC 25922 gram negative), *E. Coli* (ATCC 25922 gram positive).

2.2. Methods

2.2.1. ZnAl-Cl Synthesis

The ZnAl-LDH with a molar ratio of 2 :1 was synthesized by the co-precipitation method. About 150 ml of $ZnCl_2 \cdot 7H_2O$ (0,66M) and $AlCl_3 \cdot 6H_2O$ (0,33M) are added to a reactor initially containing 100 ml of distilled water at 25 °C under stirring. The pH of the reaction was maintained constant at 10.5 ± 0.1 with the addition of 1.5 M $NaOH$ solution under vigorous stirring. Duration of the reaction was 24 h at the ambient temperature (25°C). The precipitate obtained was washed and centrifuged several times and was dried at room temperature then crushed.

2.2.2. Synthesis of ZnAl-DDPA

The intercalation of the diamino dodecyl phosphonic acid (DDPA) was made by the method of exchange of ions by the direct reaction between the DDPA and ZnAl-Cl (Feng et al., 2006). The hybrid material was obtained by mixing the DDPA with ZnAl-LDH. Briefly, 1g of DDPA dispersion (1.736×10^{-3} M) is dissolved in 50 ml of water and mixed with 20 g for LDH [ZnAl-Cl] (Ratio 1/20). The reaction mixture is left under stirring for 24 hours. It is filtered and dried for 48 hours at the ambient temperature.

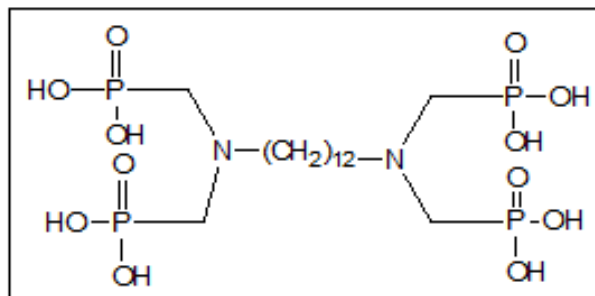


Figure 1: diamino dodecylphosphonic acid Molecule.

2.3. Characterization techniques

2.3.1. XRD Analyses

The X-ray diffraction (XRD) analysis was performed on a PAN analytical X'PERT Pro diffractometer with $CuK\alpha$ radiation (1.5405 \AA) and with an operating voltage of 40 kv and a sweeping of 2θ from 5 to 100.

2.3.2. FTIR Analyses

Fourier-transform infrared (FTIR) spectra of the samples were obtained with a Perkin-Elmer

Spectrum 16PC equipped with a thermostat.

2.3.3. BET analyses

Specific surfaces areas and pore size were analyzed by the Brunauer Emmett Teller (BET) method. Measurements were made by adsorption and thermal desorption of N₂ at 77°K and the results were collected by Quantachrome Autosorb-6.

2.3.4. Elementary analyses

Elementary analysis was carried out using a Shimadzu ICPS-7500 inductively coupled plasma (ICP) atomic emission spectroscopy.

2.4. Antibacterial activity

ZnAl-Cl and Zn-Al-DDPA antibacterial activity was examined against three test organisms, namely *E. coli* (ATCC 25922), *Streptococcus* (ATCC 25922) and *Bacillus* (ATCC 25922), by qualitative method (Mishra et al.,2017) to evaluate the potency of each sample. 0,5 ml of cultures were diluted in 20 ml of Muller Hinton liquid, this last was melted by heating and then cooled before placing in contact with the bacterial suspension. One milligram of each sample was placed at well-marked places on bacterial culture. The mixture was deposited in Petri dishes of 90 mm in the form of wells.

The inhibition zones of each sample around spots at regular intervals after 24h incubation, at 37 °C, were noticed visually.

3. Results and discussion

3.1. X-ray diffraction

The XRD patterns of the hybrid (ZnAl-DDPA) and ZnAl-LDH are presented in the figure 2 ,The basal

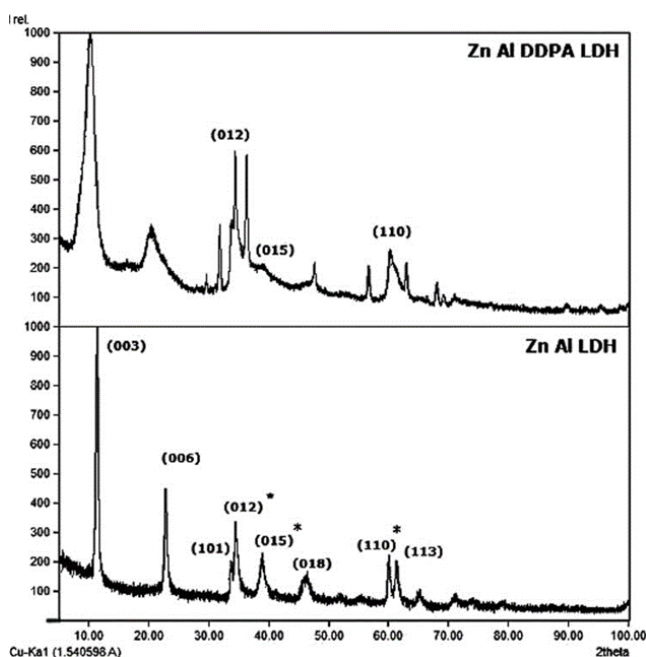


Figure 2: XRD patterns of Zn/Al-LDH and Zn/Al-DDPA.

plane spacing of the pristine LDH (Zn/Al-LDH) is 7.55 Å and an inter metallic distance of 1.53 Å. With a successful intercalation there is an increase in the basal plane of ZnAl-DDPA caused by the intercalation of DDPA, herein the spots can be indexed to a rhombohedral symmetry (space group, R-3m) (Mandal et al.,2009) and were indexed in an hexagonal structure. The (a) and (c) lattice parameters were calculated using (110) and (003) reflections, respectively.

3.2. Fourier transformed infrared spectroscopy analysis (FTIR)

Bands of Fourier transformed infrared spectroscopy (FTIR) are shown in Figure 3, the band 3458 cm⁻¹ corresponds to the stretching vibration of the hydroxide groups of the molecules water, The peaks located at 1120 and 1020 cm⁻¹ are attributed to the bending vibration of adsorbed phosphate P=O, P-O respectively (Villemin et al.,2010), showing that the pristine LDH grafted by phosphonic acid (DDPA) and the secondly significant difference between the two spectra is that there are two peaks of low intensity recorded at 2980 and 2857 cm⁻¹ which due respectively to the elongations of -CH₂ asymmetrical and symmetrical.

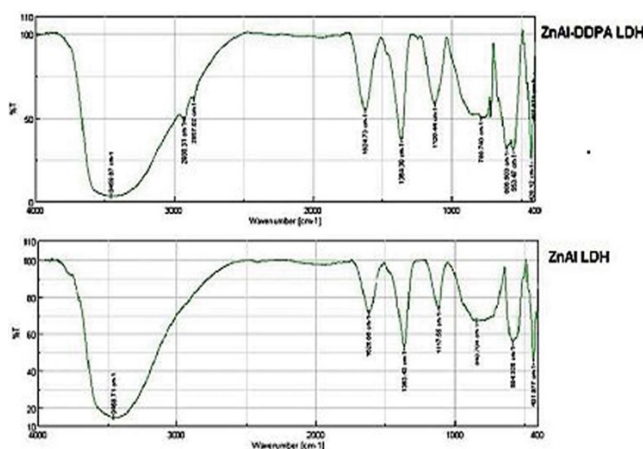


Figure 3: FTIR spectra of ZnAl-LDH and ZnAl-DDPA.

3.3. Elemental analysis and BET analysis

The molar ratio of the synthesized LDH materials was determined with use of AAS elementary analysis, and the results are given in Table 1, it can be distinguished that there are deviations between initial atomic ratios in solution and final atomic ratios were observed. It is observed from the data that some amount of Zn is being replaced by addition of DDPA to the system, and it is remarkable that the absence of Cl⁻ in the composition of LDH hybrid (ZnAl-DDPA) proves the exchange of ions between the chloride ions and the DDPA.

Specific surface areas of ZnAl-LDH and ZnAl-DDPA were estimated and presented in **Table 2**. It is evident from the table that the specific surface area (BET) decreased after DDPA intercalation in ZnAl-LDH.

3.4. Antibacterial Tests

The inhibition zones are shown in Figure 4 and the diameters of their sizes are summarized in Figure 5 and Table 3. The experiments were done three times to confirm the obtained results. The results revealed that ZnAl-Cl material sample has excellent antibacterial activity against the mentioned bacteria; presumably for the fact that ZnAl LDH presents a positive charge. This might be as a result of peptide polyglycogene existing in the cell border of gram positive bacteria and operating with plenty of pores that allowed stronger molecules to penetrate into the cell easily (Mohamed et al.,2013). Another elucidation is zinc ion, it has a magnificent effect on both bacteria (Sugarman., 1983) indicating that metallic ion-exchanged LDH diffused in water

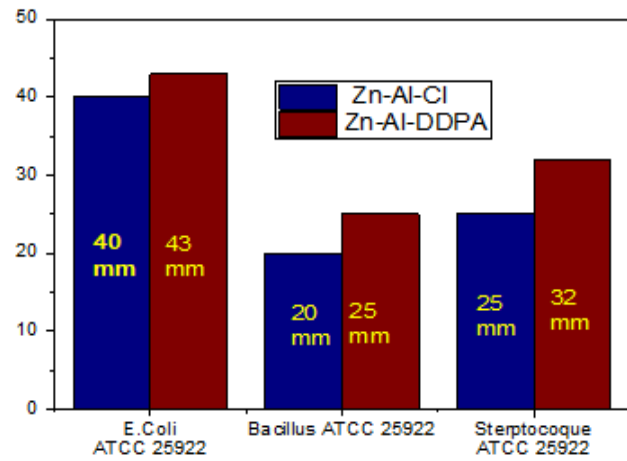


Figure 5: Histogram representing the zone of inhibition of bacterial.

attracted bacteria by electrostatic forces, which explain the perfect antibacterial activities (Dizman et al.,2007; Parolo et al.,2010).

4. Conclusion

Zn-Al LDH an Zn-Al-DDPA synthesized in the laboratory and characterized by XRD, FTIR, BET, and the

| Sample composition | Zn (wt%) | Al (wt %) | Cl (wt%) | P (wt%) | C (wt%) | Zn ²⁺ /Al ³⁺ molar ratio |
|--------------------|----------|-----------|----------|---------|---------|------------------------------------------------|
| ZnAl-LDH | 44.16 | 9.08 | 11.98 | 11.98 | — | 2.0 |
| ZnAl-DDPA | 15.48 | 3.29 | - | - | 6.01 | 1.9 |


Table 1: Chemical composition of ZnAl-LDH and ZnAl-DDPA.

| | BETsurface area(m2g-1) | Pore volume(cm3g-1) | Average pore size(nm) |
|-----------|------------------------|---------------------|-----------------------|
| ZnAl-LDH | 62.4854 | 0.2908 | 18.6157 |
| ZnAl-DDPA | 10.3297 | 0.009791 | 3.7912 |

Table 2: Pore properties and specification surface area of ZnAl-HDL and ZnAl-DDPA.

| | Bacterial strains | | |
|------------------|-----------------------------|----------------------------|----------------------------------|
| | Gram-negative | Gram-positive | |
| | <i>E.Coli</i> ATCC 25922 | <i>Bacillus</i> ATCC 25922 | <i>Sterptocoque</i> ATCC25922 |
| ZnAl-Cl | 40mm+0,5 | 20mm+0,7 | 25mm+0,1 |
| ZnAl-DDPA | 43mm+0,05 | 25mm+0,08 | 32mm+0,04 |

Table 4: Antibacterial test results of adsorbents materials ZnAl-LDH and ZnAl-DDPA against bacterial stains.

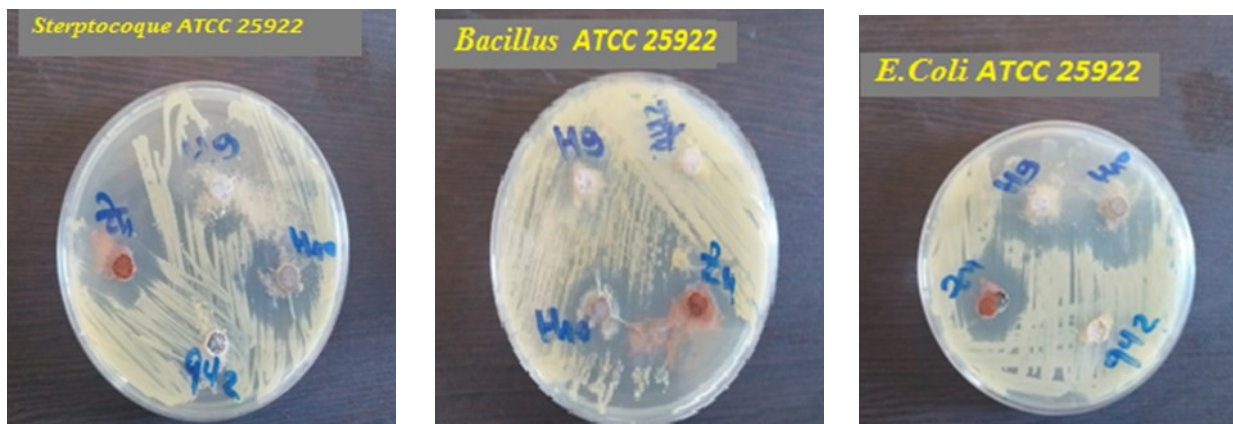

H9 :ZnAl-LDH .H10 :ZnAl-DDPA

Figure 4: Inhibition zone tests of adsorbents materials ZnAl-LDH, ZnAl-DDPA against bacterial stains

elementary analysis showed high antibacterial activity against all the tested microorganisms such as *E.coli* (ATCC 25922), *Streptococcus* (ATCC 25922), *Bacillus* (ATCC 25922). The antibacterial activity was evaluated with respect to the inhibition zone size in mm, therefore, this hybrid material exhibited very good antibacterial potency, and such a result gives evidence of the feasibility of the samples as “active antibacterial” materials.

Acknowledgements

This work was supported by Dr Moulay Tahar University, Saida, Algeria and “PunchOrga” Network (Pole Universitaire Normand de Chimie Organique), the “Ministère de la Recherche et des Nouvelles Technologies,” CNRS (Centre National de la Recherche Scientifique).

References

- Chen C, Gunawan P, Xu R (2011) Self-assembled Fe₃O₄-layered double hydroxide colloidal nanohybrids with excellent performance for treatment of organic dyes in water. *Journal of Materials Chemistry* 21(4): 1218-1225.
- Cheng H M, Gao X W, Zhang K, Wang X R, Zhou W, et al. (2019) A novel antimicrobial composite: ZnAl-hydrotalcite with p-hydroxybenzoic acid intercalation and its possible application as a food packaging material. *New Journal of Chemistry* 43(48): 19408-19414.
- Dizman B, Badger JC, Elasmir MO, Mathias LJ (2007) Antibacterial fluoromicas: A novel delivery medium. *Applied Clay Science* 38(1-2): 57-63.
- Feng Y, Li D, Wang Y, Evans D G, Duan X (2006) Synthesis and characterization of a UV absorbent-intercalated Zn-Al layered double hydroxide. *Polymer Degradation and Stability* 91(4): 789-794.
- Ferraris S, Spriano SJMS (2016) Antibacterial titanium surfaces for medical implants. *Materials Science and Engineering C* 61: 965-978.
- Gohi BFCA, Zeng HY, Cao XJ, Zou KM, Shuai W, Diao Y (2019) Preparation of the hybrids of hydrotalcites and chitosan by urea method and their antimicrobial activities. *Polymers* 11(10): 1588.
- Huo K, Zhang X, Wang H, Zhao L, Liu X, & Chu P K (2013) Osteogenic activity and antibacterial effects on titanium surfaces modified with Zn-incorporated nanotube arrays. *Biomaterials* 34(13): 3467-3478.
- Kadari M, Kaid MH, Ben Ali M, & Villemin D (2017) Selective study of elimination of Cd (II) and Pb (II) from aqueous solution by novel hybrid material. *Journal of the Chinese Advanced Materials Society* 5(3): 149-157.
- Marcato PD, Parizotto NV, Martinez DST, Paula AJ, Ferreira IR, Melo PS, & Alves O L (2013) New hybrid material based on layered double hydroxides and biogenic silver nanoparticles: antimicrobial activity and cytotoxic effect. *Journal of the Brazilian Chemical Society* 24(2): 266-272.
- Mandal S, Mayadevi S (2009) Defluoridation of water using as-synthesized Zn/Al/Cl anionic clay adsorbent: Equilibrium and regeneration studies. *Journal of Hazardous Materials* 167(1-3): 873-878.
- Mei X, Ma J, Bai X, Zhang X, Zhang S, Liang R, Duan X (2018) A bottom-up synthesis of rare-earth-hydrotalcite monolayer nanosheets toward multimode imaging and synergetic therapy. *Chemical science* 9(25): 5630-5639.
- Mishra G, Dash B, Sethi D, Pandey S, Mishra BK (2017) Orientation of organic anions in Zn-Al layered double hydroxides with enhanced antibacterial property. *Environmental Engineering Science* 34(7): 516-527.
- Mishra G, Dash B, Pandey S, & Sethi D (2018) Ternary layered double hydroxides (LDH) based on Cu-substituted ZnAl for the design of efficient antibacterial ceramics. *Applied Clay Science* 165: 214-222.
- Mishra G, Dash B, Pandey S (2018) Layered double hydroxides: A brief review from fundamentals to application as evolving biomaterials. *Applied Clay Science* 153: 172-186.
- Mohamed NA, Sabaa MW, El-Ghandour AH, Abdel-Aziz MM, Abdel-Gawad OF (2013) Quaternized N-substituted carboxymethyl chitosan derivatives as antimicrobial agents. *International Journal of Biological Macromolecules* 60: 156-164.
- Parolo ME, Avena MJ, Pettinari G, Zajonkovsky I, Valles JM, & Baschini MT (2010) Antimicrobial properties of tetracycline and minocycline-montmorillonites. *Applied Clay Science* 49(3): 194-199.
- Ryu SJ, Jung H, Oh JM, Lee JK, & Choy JH (2010) Layered double hydroxide as novel antibacterial drug delivery system. *Journal of Physics and Chemistry of Solids* 71(4): 685-688.
- Sugarman B (1983) Zinc and infection. *Reviews of infectious diseases* 5(1): 137-147.
- Totaro G, Sisti L, Celli A, Aloisio I, Di Gioia D, Marek AA, Leroux F (2018) Dual chain extension effect and antibacterial properties of biomolecules interleaved within LDH dispersed into PBS by in situ polymerization. *Dalton Transactions* 47(9): 3155-3165.
- Villemin D, Moreau B, Kaid MH, & Didi MA (2010) Rapid one-pot synthesis of alkane- α , ω -diylbisphosphonic acids from dihalogenoalkanes under microwave irradiation. *Phosphorus, Sulfur and Silicon* 185(8): 1583-1586.
- Wang M, Hu Q, Liang D, Li Y, Li S, Zhang X, Yang X (2013) Intercalation of Ga³⁺-salicylidene-amino acid Schiff base complexes into layered double hydroxides: synthesis, characterization, acid resistant property, in vitro release kinetics and antimicrobial activity. *Applied clay science* 83: 182-190.
- Wang X, Liu S, Li M, Yu P, Chu X, Li L, Ning C (2016) The synergistic antibacterial activity and mechanism of multicomponent metal ions-containing aqueous solutions against *Staphylococcus aureus*. *Journal of Inorganic Biochemistry* 163: 214-220.
- Zümreoglu-Karan B, Ay A (2012) Layered double hydroxides—multifunctional nanomaterials. *Chemical Papers* 66(1): 1-10.